

ESKY[®] LOS 2343

Pioneer Hot Work
Tool steel resistant
to thermal fatigue and
to high-temperature wear
in ESR quality

General characteristics

EsKyLos[®] 2343 is the pioneer of the high alloyed Chromium-Molybdenum-Vanadium Hot Work Tool steels, suited designed for the manufacturing of dies, moulds, punches and other components subjected to high working temperatures.

The best features of this pioneer steel grade are:

- high resistance to thermal shock and to heat cracking;
- good mechanical characteristics in hot and cold conditions;
- excellent toughness in hot and cold conditions;
- resistance to temper;
- excellent machinability.

The combination of these characteristics guarantees excellent TLCC (Total Life Cycle Cost) of the tool. For this reason, EsKyLos[®] 2343 is the pioneer of the Hot Work tool steels, one of the most used and appreciated steels for the production of dies and moulds subjected to high working temperature.

EsKyLos[®] 2343 is obtained through a special 'super clean' manufacturing process, which allows a high level of micro-purity.

EsKyLos[®] 2343 is normally supplied in sections up to 500 mm in thickness, in the annealed condition with hardness values lower than 220 HB, thereby guaranteeing a good machinability.

If subjected to suitable hardening, followed by at least two suitable tempers, EsKyLos[®] 2343 can reach a hardness up to 50 HRC without strongly affecting the toughness.

In order to improve further the mechanical characteristics of the surface, EsKyLos[®] 2343 can be coated with PVD or PA/CVD methods. Alternatively it can be subjected to nitriding; this allows a hardness value of the nitrided layer about 900-1000 HV.

The high micro-purity and structural homogeneity levels give this grade good suitability to mirror polishing and photo-engraving.

If required, it is possible to carry out welding operations with TIG or MMA methods on dies made of EsKyLos[®] 2343.

Constant development in hot processing technologies require the use of EsKyLos[®] 2343, thanks to its high resistance to thermal fatigue and high temperature wear.

Thanks to its quasi-isotropic properties of ESR quality, EsKyLos[®] 2343 represents also one of the most important tough options for highly resistant plastic moulds that need very high pressure strength, excellent resistance to abrasion, also in combination with different surface coatings, and improved toughness in the mean time.

The increasing in the use of synthetic and abrasive materials has led manufacturers to use EsKyLos[®] 2343 also when suitability for polishing and graining, combined with abrasion and compression resistance, are required.

EsKyLos[®] 2343 is 100% ultrasonically inspected, according to the most demanding of NDT standards.

It is difficult to predict the improvement that a innovative material will provide over the traditional one: it's only the feedback from service and the cooperation with customers that can validate the longer mould life of the proposed materials.

EsKyLos[®] 2343 is demonstrating impressive resistance to fatigue in many applications and a significantly longer mould life than conventional Hot Work Tool steel grades.

Continuous improvement of materials technology is managed in safety and in accordance with eco-consistency and sustainability criteria, because Lucchini RS believes that Safety and Environment are the main priorities in all the phases of the manufacturing process.

EsKyLos[®] 2343 is also designed with the aim to guarantee the minimum use of virgin materials, moving toward the use of scrap categories, difficult to be recycled, that can become food for the steel making production of EsKyLos[®] 2343 grade.

Chemical analysis

| | Range | C [%] | Si [%] | Mn [%] | Cr [%] | Mo [%] | V [%] | S [%] | P [%] |
|---|-------|-------|--------|--------|--------|--------|-------|-------|-------|
|  Alloying [% in weight] | min | 0,35 | 0,80 | 0,30 | 5,00 | 1,20 | 0,30 | - | - |
| | max | 0,40 | 1,10 | 0,50 | 5,50 | 1,50 | 0,50 | 0,003 | 0,015 |

Table for comparison of international classification

| | |
|---------------|----------------------|
| W. Nr. | 1.2343 |
| DIN | X38CrMoV5-1 |
| AFNOR | Z38CDV5 |
| AISI | H11 |
| UNI | X37CrMoV5.1KU |

Heat analysis obtained during the pouring of the steel: in accordance with NADCA #207 PUBLICATION #229, as show in the table.

Product analysis: in order to consider the possible deviations due to the analytical reproducibility and the heterogeneity of the steel, the range of the chemical composition applicable to product analysis is usually wider than the one applicable to the heat analysis for C and Cr values. This point is regulated by the Table 6 of DIN 17 350.

Lucchini RS's tool steels have been researched and formulated in order to optimize the material performances.

The brand name identifies the Lucchini RS product and the number evokes the Werkstoff classification or other means of reflecting the characteristics of use.

Main applications

EskyLos[®] 2343 is suitable for the following applications:

- dies for aluminium die-casting
- dies subjected to low pressure
- chill moulds for gravity casting
- containers for die-casting presses
- dies for aluminium extrusion
- extrusion press blocks
- sleeves for extrusion presses
- injection moulds.

Physical and mechanical properties


Main physical properties

| ESKY[®] LOS 2343 | 20°C | 400°C | 600°C |
|--|------|-------|-------|
| Modulus of elasticity [GPa] (1GPa=1000 MPa) | 210 | 183 | 168 |
| Coefficient of thermal expansion from 20 °C at [10 ⁻⁶ /K] | - | 11,8 | 12,4 |
| Thermal conductivity [W/mK] | 24,4 | 27,1 | 28,5 |

Main mechanical properties

| ESKY[®] LOS 2343 | 400°C | 500°C | 600°C |
|---------------------------------------|-------|-------|-------|
| Ultimate Tensile strength (UTS) [MPa] | 1.150 | 950 | 670 |
| Yield stress (YS) [MPa] | 900 | 750 | 470 |

These are average obtained on a sample which has been hardened at 980 °C, quenched and tempered at 600 °C to achieve a hardness of 44 HRc.

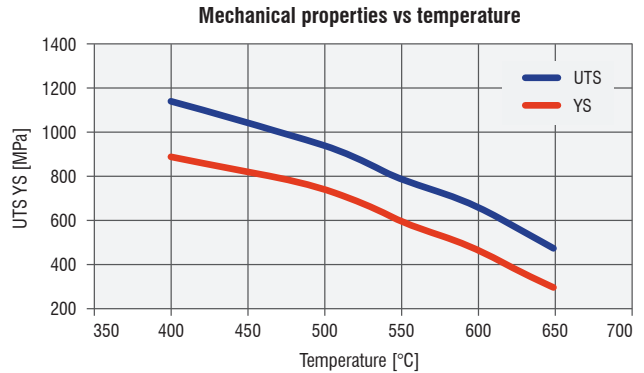

Heat treatments

EskyLos[®] 2343 is supplied in the annealed condition. If a different hardness is required or if heat treatment is needed, we suggest applying the following parameters.

This information is only indicative and must be adapted depending on the different heat treatment facilities employed and on the thickness of the bar: for any question and particular requirement don't hesitate to contact our technical staff of Metallurgy & Laboratories Department.

Soft annealing

| | |
|-----------------------|--|
| Suggested temperature | 850 °C |
| Heating | Max 50 °C/h |
| Soaking time | Minimum 120 min from when the temperature settles |
| Cooling | Slow in the furnace at max 25 °C/h to 600 °C , then at room temperature |

Soft annealing is recommended if optimum machinability of the material is important. After soft annealing a hardness of around 220 HB is achieved.

Stress Relieving

| | |
|-----------------------|---|
| Suggested temperature | 650 °C |
| Heating | Max 100 °C/h |
| Soaking time | Minimum 120 min from when the temperature settles |
| Cooling | Slow in the furnace at max 25 °C/h to 200°C , then at room temperature |

If the suggested temperature is lower than the tempering temperature, the stress relieving temperature will be 50° C lower than the tempering temperature previously applied.

Stress relieving is recommended where it is necessary to eliminate residual stresses induced by mechanical working or by a preceding heat treatment.

Hardening

Hardening should be carried out after the material has been pre-heated according to the following table.

| | |
|-------------------------------|--|
| First pre-heating temperature | 400 °C |
| Heating | Max 150 °C/h |
| Soaking time | 25 min every 25 mm thickness or when (Ts-Tc) < 90 °C |

| | |
|--------------------------------|--|
| Second pre-heating temperature | 600 °C |
| Heating | Max 150 °C/h |
| Soaking time | 20 min every 25 mm thickness or when (Ts-Tc) < 90 °C |

| | |
|-------------------------------|--|
| Third pre-heating temperature | 800 °C |
| Heating | Max 150 °C/h |
| Soaking time | 20 min every 25 mm thickness or when (Ts-Tc) < 90 °C |

| | |
|---------------------------|--|
| Austenitizing temperature | 980-1010 °C |
| Heating | > 150°C/h |
| Soaking time | $t = (x + 39) / 2$ or 30 min from when (Ts-Tc) < 15 °C |
| Cooling | Air, vacuum cooling, salt bath, polymer in H2O |
| Hardness after quenching | 54 ÷ 55 HRc |

We suggest to carry out hardening on material supplied in the annealed condition and tempering immediately afterwards.

The aim of the first pre-heat at 400 °C is to eliminate stresses caused by machining. The following pre-heating cycles at 600 °C and 800 °C are necessary to homogenise the temperature of the piece. We recommend a rate of heating of 150 °C/h max.

The time of the different stages of pre-heating is calculated on the basis of the thickness of the piece and the temperature, as shown on the table.

Alternatively, the time can be adjusted on the basis of the difference between the internal temperature (Tc) and the Surface temperature (Ts) of the piece, measured by means of two thermocouples.

After the third pre-heat at 800 °C, the austenitising temperature should be reached as quickly as possible and maintained for 30 min from when (Ts-Tc) < 15 °C or on the basis of the following formula:

$$t = (x + 39) / 2$$

t = soaking time [min]
x = thickness [mm]

Tempering

It is recommended to set the temperature of the first temper at 580 °C, close to the secondary hardness.

The temperature of the second temper must be set on the basis of the required mechanical properties, and must be higher than the temperature applied for the first temper.

The soaking time for the first and the second temper are calculated by applying the following empirical formula:

$$t' = t'' = 0,8 x + 120$$

$t' = t''$ = soaking time [min]
 x = thickness [mm]

| | |
|-----------------------------|--------------------|
| First tempering temperature | 550 - 580 °C |
| Soaking time | $t' = 0,8 x + 120$ |
| Cooling | Room temperature |

| | |
|------------------------------|---|
| Second tempering temperature | Set on the basis of the required mechanical properties, in any case higher than the temperature applied for the first temper. |
| Soaking time | $t'' = 0,8 x + 120$ |
| Cooling | Room temperature |

A third temper at a temperature of 30-50 °C below the maximum temperature previously applied will function as a stress relieving cycle.


Tempers at a temperature between 400 and 550 °C are not advisable, as they reduce the material toughness. Tempers at a temperature lower than 200 °C should not be carried out.

The soaking time for the third temper are calculated by applying the following empirical formula:

$$t''' = 0,8 x + 180$$

t''' = soaking time [min]
 x = thickness [mm]

| | |
|-----------------------------|--|
| Third tempering temperature | 30-50 °C lower than the max temperature previously applied |
| Soaking time | $t''' = 0,8 x + 180$ |
| Cooling | Slow cooling in the furnace up to 250 °C, then at room temperature |

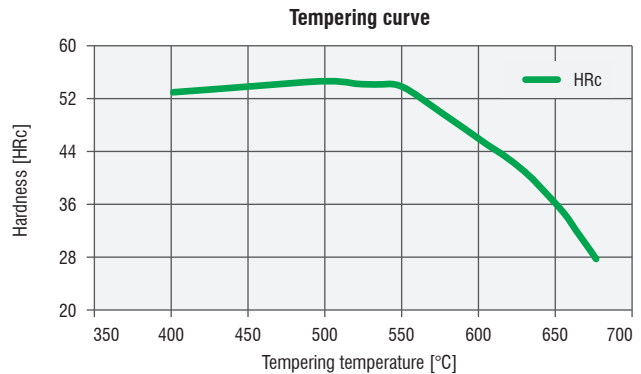

Tempering curve of a sample which has been austenitised at 980 °C. The diagram shows values obtained after the second temper.

Variation in dimensions during heat treatment

During the heat treatment of EskyLos[®] 2343 the phase transformation points are exceeded. Inevitably this causes a variation in the volume of the material. For this reason we recommend leaving enough machining allowance to compensate for the change of dimension due to heat treatment. All the corners should be rounded off.

Nitriding

The purpose of nitriding is to increase the resistance of the material to wear and abrasion. This treatment is very useful for components where high performance is necessary, as it extends the life of the material. We suggest nitriding the component in the hardened and tempered condition. The tempering temperature must be at least 50 °C higher than the nitriding temperature.

Modern nitriding processes allow the original dimensions of the component to be maintained. We recommend heat treating the component in the finish machined condition.

Remarks


In accordance with its internal technical instruction I.T. MET U002 Lucchini RS has selected highly specialized heat treatment companies, which perform the vacuum hardening complying with Lucchini RS heat treatment procedure I.T.MET – U001.

We strongly recommend to send your dies to one of the heat treatment companies officially approved by Lucchini RS.


For more information don't hesitate to ask to our local Distributor – Service Center or to our Sales Department. In case of different needs of heat treatment (like salt bath) please contact our technical staff of Metallurgy & Laboratories Department.

In any case, other properties can be analysed and studied deeper by Lucchini RS on specific Customer request: please consult Lucchini RS specialists of MET Department.

CCT Curve

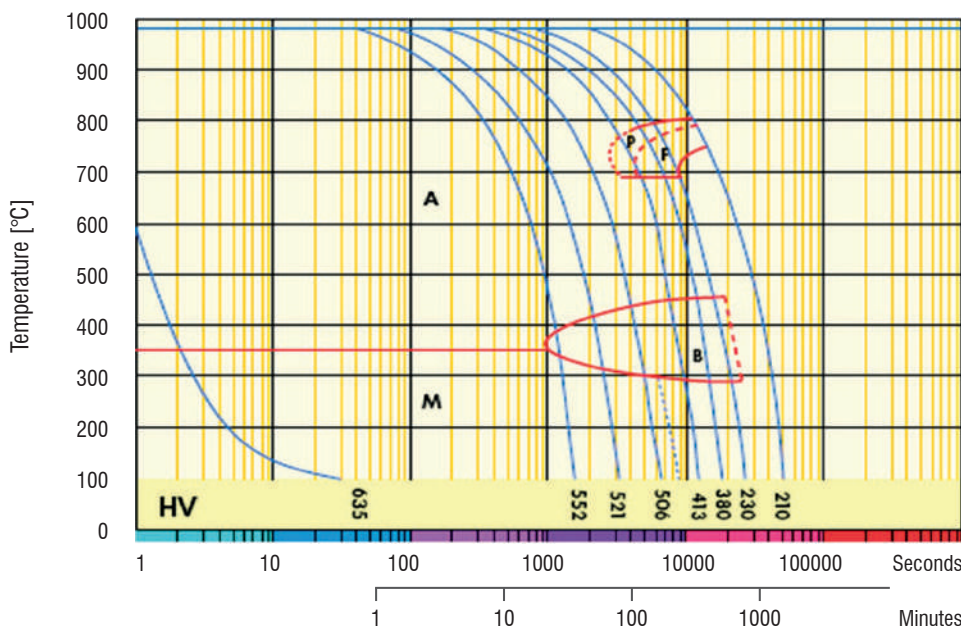


Annealed microstructure of Eskylos[®] 2343

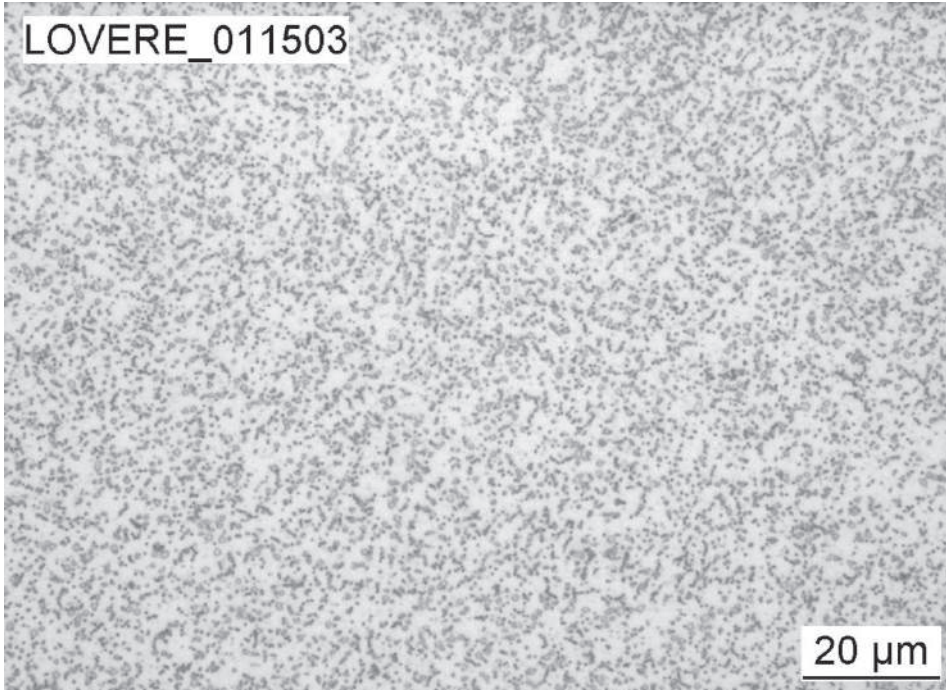

The annealed microstructure of the as received steel consists essentially of a ferritic matrix with a homogeneous distribution of spheroidized carbides, when examined at 500X, after being polished and etched with 4% Nital, free of excessive banding.

Comparison of properties of different hot work tool steels

The following table shows a quick comparison among the most important characteristics of the Hot Work tool Steel grades produced by Lucchini RS.

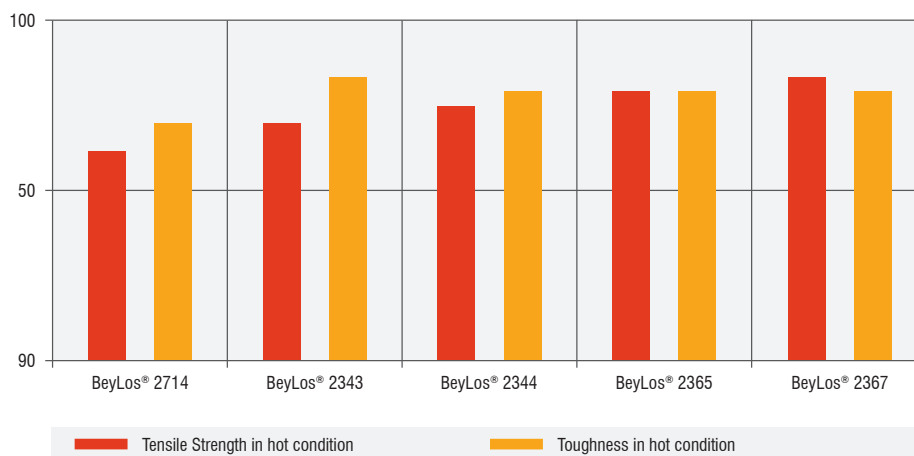

Quick comparison guide among the different Hot Work Tool Steel Grades

The following table shows a quick comparison among the most important characteristics of the Hot Work tool Steel grades produced by Lucchini RS.

| Lucchini RS Hot Work tool Steel Family | | | | | | | | | | | | | | | |
|--|----------------------------------|------------|------------|------------|------------|------------|------------|------------|------------|------------|------------|------------|------------|------------|------------|
| Special features and delivered conditions | Annealed Not Corrosion Resistant | | | | | | | | | | | | | | |
| | KEYLOS | BEYLOS | | | | | | | | ESKYLOS | | | | | |
| | 6959 | 2329 | 2711 | 2714 | 2340 | 2343 | 2344 | 2365M | 2367 | 6959 | 2340 | 2343 | 2344 | 2365M | 2367 |
| HB in surface In Annealed condition | <220 | <220 | <220 | <220 | <220 | <220 | <220 | <220 | <220 | <220 | <220 | <220 | <220 | <220 | <220 |
| HB in surface Hardened after machining | 370 410 | 370 410 | 370 410 | 370 410 | 400 450 | 400 450 | 400 450 | 400 450 | 400 450 | 370 410 | 400 450 | 400 450 | 400 450 | 400 450 | 400 450 |
| Maximum thickness [mm] | 500 | 600 | 500 | 700 | 500 | 500 | 500 | 500 | 500 | 500 | 500 | 500 | 500 | 500 | 500 |
| Hardness and Wear Resistance | 3 | 3 | 3 | 3 | 4 | 4 | 4 | 4 | 4 | 3 | 4 | 4 | 4 | 4 | 4 |
| Degree of Through Hardening in the section | 4 | 2 | 3 | 3 | 3 | 3 | 3 | 3 | 3 | 4 | 3 | 3 | 3 | 3 | 3 |
| Toughness | 4 | 1 | 4 | 4 | 3 | 3 | 2 | 2 | 2 | 4 | 3 | 3 | 2 | 2 | 2 |
| Machinability after Annealing | 3 | 3 | 3 | 3 | 3 | 3 | 3 | 3 | 3 | 3 | 3 | 3 | 3 | 3 | 3 |
| Machinability after Hardening | 1 | 2 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 |
| Etch-Grainability | 2 | 2 | 2 | 2 | 2 | 2 | 2 | 2 | 2 | 4 | 4 | 4 | 4 | 4 | 4 |
| Polishability | 2 | 2 | 2 | 2 | 2 | 2 | 2 | 2 | 2 | 4 | 4 | 3 | 3 | 4 | 3 |
| Repair by Welding | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 |
| Thermal Conductivity | 2 | 2 | 2 | 2 | 1 | 1 | 1 | 1 | 1 | 2 | 1 | 1 | 1 | 1 | 1 |
| Corrosion Resistance | 0 | 0 | 0 | 0 | 0 | 0 | 0 | 0 | 0 | 0 | 0 | 0 | 0 | 0 | 0 |

4 Excellent 3 Very Good 2 Good 1 Normal 0 Unsuitable

The information and the data presented here are typical or average values and are not a guarantee of maximum or minimum values.

Applications specifically suggested for materials described herein and in the quick comparison guide among the different grades are made solely for the purpose of illustration to enable the reader to make his own evaluation and are not intended as warranties, either express or implied, of fitness for these or other purposes.

The advantages of the ESR technology

The ESR (Electro-Slag-Melting) manufacturing technology offers the following advantages:




- increase of material toughness;
- high micro-cleanness level;
- total isotropy of the material;
- very low segregation level.



The ESR process is based on ingot remelting, through a traditional VD (vacuum degassing) process, using a particular copper ingot mould that contains basic slag.

The ingot is remelted in a way that the liquid metal passes through the slag, which acts as a filter and retains the inclusions.


The process of solidification inside the ingot mould is faster than in a traditional process.

The result is homogeneous and isotropic steel.

| | |
|---|---|
|  | Moulds painted or transparent plastic components for automotive sector. Moulds for cars' trims, cars' head-rear lights, lenses. |
|  | Special version dedicated to high pressure Al & Mg Die-Casting according to SEP1614.96 / VDG M82-1993 specifications. |
|  | New version designed for the strictest application of high pressure Al & Mg Die-Casting according to NADCA specification #229. |

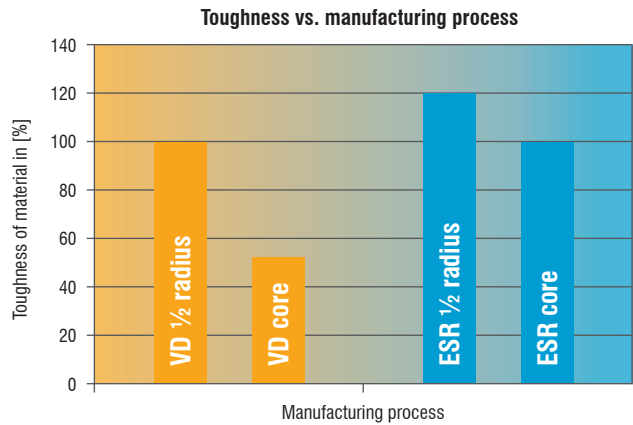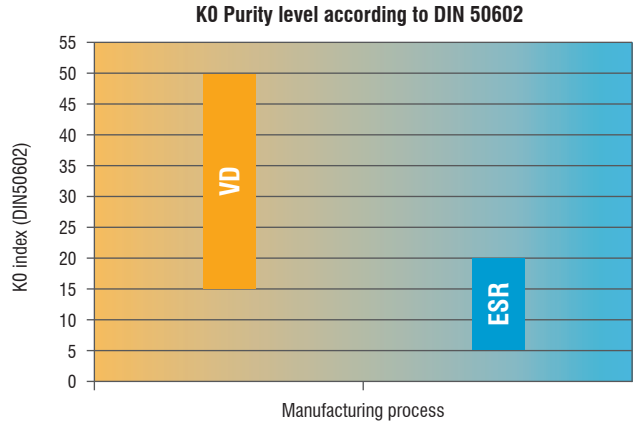

Thanks to the ESR process, EskyLos[®] 2343 satisfies the most difficult requirements in terms of toughness and suitability to polishing. It is suitable for the manufacture of moulds subjected to mirror polishing and to high mechanical stress.

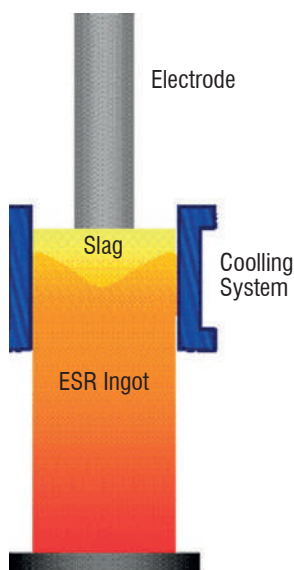

Guidance for machining

The following parameters are indicative only and must be adapted to the particular application and to the machinery employed. The data refer to material in the annealed condition. Hardness 220 HB max.

Turning

| Type of insert | Rough machining | | Finish machining | |
|-----------------------------|-----------------|-----|------------------|-----------|
| | P20-P40 coated | HSS | P10-P20 coated | Cermet |
| V_c cutting speed [m/min] | 170 ÷ 220 | (*) | 200 ÷ 250 | 240 ÷ 300 |
| a_r cutting depth [mm] | 1 ÷ 5 | (*) | < 1 | < 0,5 |

Milling

| Type of insert | Rough machining | | |
|-----------------------------|--------------------|----------------|-----|
| | P25-P35 not coated | P25-P35 coated | HSS |
| V_c cutting speed [m/min] | 160 ÷ 240 | 180 ÷ 280 | (*) |
| f_z feed [mm] | 0,15 ÷ 0,3 | 0,15 ÷ 0,3 | (*) |
| a_r cutting depth [mm] | 2 ÷ 4 | 2 ÷ 4 | (*) |

| Type of insert | Pre-finishing | | |
|-----------------------------|--------------------|----------------|-----|
| | P10-P20 not coated | P10-P20 coated | HSS |
| V_c cutting speed [m/min] | 180 ÷ 260 | 200 ÷ 280 | (*) |
| f_z feed [mm] | 0,2 ÷ 0,3 | 0,2 ÷ 0,3 | (*) |
| a_r cutting depth [mm] | 1 ÷ 2 | 1 ÷ 2 | (*) |

| Type of insert | Finishing | | |
|-----------------------------|--------------------|----------------|------------|
| | P10-P20 not coated | P10-P20 coated | Cermet P15 |
| V_c cutting speed [m/min] | 200 ÷ 280 | 220 ÷ 300 | 240 ÷ 330 |
| f_z feed [mm] | 0,05 ÷ 0,2 | 0,05 ÷ 0,2 | 0,05 ÷ 0,2 |
| a_r cutting depth [mm] | 0,5 ÷ 1 | 0,5 ÷ 1 | 0,3 ÷ 0,5 |

(*) not advisable

Drilling

| Type of insert | tip with interchangeable inserts | HSS | brazed tip |
|-------------------------------|----------------------------------|-----|-------------|
| V_c cutting speed [m/min] | 190 ÷ 220 | (*) | 60 ÷ 80 |
| f_z feed per turn [mm/turn] | 0,05 ÷ 0,15 | (*) | 0,15 ÷ 0,25 |

(*) not advisable

General formulae

| Type of machining | Drilling | Milling |
|-------------------------------|---|--|
| n: number of turns of mandrel | $V_c * 1000 / \pi * D_c$ | $V_c * 1000 / \pi * D_c$ |
| V_f : feed speed [m/min] | $V_f = f_z * n$ | $V_f = f_z * n * z_n$ |
| f_z feed per turn [mm/turn] | - | $f_n = V_f / n$ |
| Note | D_c : Milling cutter or tip diameter [mm] V_c : cutting speed [m/min] f_z : feed [mm] | f_n : feed per turn [mm/turn] z_n : No. of milling cutter inserts |

Approximate equivalent values between hardness and ultimate tensile strength

| | | | | | | | | | | | | | |
|-----|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| HB | 530 | 520 | 512 | 495 | 480 | 471 | 458 | 445 | 430 | 415 | 405 | 390 | 375 |
| HRc | 54 | 53 | 52 | 51,1 | 50,2 | 49,1 | 48,2 | 47 | 45,9 | 44,5 | 43,6 | 41,8 | 40,5 |
| MPa | 1.900 | 1.850 | 1.800 | 1.750 | 1.700 | 1.650 | 1.600 | 1.550 | 1.500 | 1.450 | 1.400 | 1.350 | 1.300 |

| | | | | | | | | | | | | | |
|-----|-------|-------|-------|-------|-------|-------|-----|-----|-----|-----|-----|-----|-----|
| HB | 360 | 350 | 330 | 320 | 305 | 294 | 284 | 265 | 252 | 238 | 225 | 209 | 195 |
| HRc | 38,8 | 37,6 | 35,5 | 34,2 | 32,4 | 31 | 29 | 27 | -- | -- | -- | -- | -- |
| MPa | 1.250 | 1.200 | 1.150 | 1.100 | 1.050 | 1.000 | 950 | 900 | 850 | 800 | 750 | 700 | 650 |

Welding

Welding of EskyLos® 2343 can give good results if the recommended procedure is followed. Being steel with high Carbon Equivalent content, EskyLos® 2343 is very sensitive to cracking. We recommend carrying out pre-heating and heat treatment after welding.

| | | |
|----------------------------|---|-----|
| Condition of material | Annealed with hardness 220 HB max | |
| Welding technique | TIG | MMA |
| Pre-heating at | 330 ÷ 380 °C | |
| Recommended heat treatment | Heating of the material at 850 °C, cooling in the furnace to 600 °C at a rate of 20 °C/h, cooling at room temperature | |
| Condition of material | Hardened and tempered | |
| Welding technique | TIG | MMA |
| Pre-heating at | 330 ÷ 380 °C | |
| Recommended heat treatment | 650 °C or 50 °C lower than the tempering temperature previously applied | |

Electrical Discharge Machining (EDM)

EskyLos® 2343 can be machined by EDM to obtain complex shape.

Afterwards it is advisable to stress relieving the material.

Chrome Plating

EskyLos® 2343 can be Chrome plated in order to enhance the mechanical characteristics on the surface.

Within 4 hours of Chrome plating, in order to prevent Hydrogen embitterment it is advisable to carry out heat treatment at 200 °C for about 4 hours.

Photo-engraving

Thanks to modern production processes and to the low Sulphur content, EskyLos® 2343 is suitable for photo-engraving to obtain various patterns.

Polishing

EskyLos® 2343 is particularly suitable for mirror polishing, due to the ESR process.

Process and materials selection for product recyclability

According to the potential of steel recycling, Lucchini RS is adopting a strategy for environmental excellence in designing and manufacturing of its tool steel grades, putting eco-effectiveness into practice.

The main adopted steps are:

- conducting an environmental assessment on processes and products, with the minimum use of virgin materials and non-renewable forms of energy;
- moving toward zero-waste manufacturing processes, considering that the ultimate destiny of a scrapped steel mould becomes food for the next steel making process, that is the "waste equals food" philosophy;
- conducting a life cycle assessment for each product and process, minimizing the environmental cost of product and service over its entire life cycles, from creation to disposal, that is the "Cradle to Cradle" philosophy.